

## Analysis of Modified Bitumen Difference Polymers

Arthur Onischenko, Mykolay Kuzminets, Sergiy Aksenov

National Transport University, str. Suvorova 1, Kyiv, Ukraine, 01001  
e-mail: Artur\_onish@bigmir.net, Vectral6i@i.ua, Kabysik@bigmir.net

**Summary.** An important step in the preparation of modified bitumen is selection of the composition and verification of various polymers' effectiveness. Therefore, paddle mixers are widespread in both industrial and laboratory conditions for efficient mixing of bitumen with polymers. The developed method allows to determine the completion time of modification process at various process parameters (temperature, mixing speed and content of the modifier) to complete stabilization of the properties and the homogenization of bitumen. The results of studies showed that optimal time for bitumen modification at which take place both stabilization of the properties and homogenization, ie astringent take the necessary level of uniformity with latex Butonal NS198, is about 3 hours.

**Key words:** cracking resistance, rutting resistance, shear resistance, water resistance, polymer-modified bitumen, laboratory blade mixer, homogenization.

### INTRODUCTION

Roads of Ukraine are characterized by high traffic volumes and intensity, and significant dynamic load on pavement of bridges and airfields require increased requirements to asphalt concrete, and, correspondingly, to bitumen. The most common and effective way to increase quality of asphalt is use of bitumens modified with polymers which significantly improve the properties of asphalt, namely cracking resistance, rutting resistance, shear resistance and water resistance, etc. [1-3, 7-14].

An important step in the preparation of modified bitumen is selection of the composition and verification of various polymers' effectiveness. These issues require availability of appropriate laboratory mixers for making polymer-modified bitumens. Modern practice of laboratory tests of modified bitumen shows lack of standardized procedures in the laboratory mixing and related laboratory equipment, which does not allow to get polymer-modified

bitumens in compliance with sole preparation technology, whereby it is possible to get no reliable laboratory test results [2-4].

The most simple and quite effective technical means of mixing low-viscosity liquids and liquids with solids that are in a state of near suspension are blade mixers. Therefore, blade mixers are widely used, in both industrial and laboratory conditions for efficient polymer bitumen modification.

### ANALYSIS OF RECENT RESEARCH

Objective to develop methodology for preparation of polymer modified bitumen with use of laboratory blade mixer with the purpose of selection of its composition and establishment of requirements to the process of mixing.

The authors developed method of preparation of modified bitumen using laboratory blade mixer Fig. 1. [1]). Method to determine the time of completion of modification process at different process parameters (tempera-

ture, mixing speed and amount of modifier) to complete homogenization and stabilization properties of bitumen.

The technique is to set a time during modified bituminous binder, wherein the stabilization properties will, and homogenization, i.e. binder acquires desired level of uniformity. At the beginning of bitumen modification process polymer is fed and time of modification completion is set. Estimation of bitumen stabilizing properties and homogenization when feeding polymer is carried out by the following criteria:

- rate of penetration change (with additional 1 hour of bitumen modification)  $\leq 2x0$ , 1 mm / hour (modified bitumen acquired penetration stabilization),

- rate of elasticity change (with additional 1 hour of bitumen modification)  $\leq 2\% / h$  (modified bitumen acquired elasticity stabilization),


- variation coefficient in terms of penetration and elasticity (with additional 1 hour of bitumen modification)  $\leq 2\%$  (modified bitumen acquired penetration and elasticity uniformity).

Sampling schedule of modifying bitumen polymer is set taking into account stabilization properties of the binder and its homogenization. If the nature of such rates is not known for certain polymer-modified bitumen, it is recommended to carry out a trial modification, to establish nature and pace of modifications to select the appropriate sampling schedule.

Modification completion time is assumed to be the time at which all the processes of bitumen stabilization and homogenization have taken place. In order to define this time laboratory tests for definition of penetration and elasticity, their coefficients of variation at different sampling times are held. Based on the results changes of these indicators in each period between the time the mixing of sampling are assessed. Completion of the modification time is defined on the basis of the achievement of stability and uniformity properties of polymer-modified bitumen, in accordance with the scheme shown in (Fig. 2 – 5).


**Table 1.** Technical peculiarities of laboratory blade mixer

Peculiarities (conditions)	Technical data
Metal zinc container, dm <sup>3</sup> (DSTU 3277)	7
Number of agitator blades	4
Angle of the blades, degrees	90
Helix angle of the blades, degrees	22
Dimensions of blades, mm	L = 100, H = 20
The minimum distance between blades, at least, mm- Between the wall - Between the tank bottom	15 50
Frequency of rotation of blade shaft, rot / min.	10...30
Electric motor with speed control, power, kW	2
Oil electric tensor with electric temperature range, °C (GOST 13268)	from 0 to 250
Thermocouples GOST R 8.585 with temperature range, °C	from 0 to 300
Heating of the oil thermostat to a temperature T, °C	220
Heat-resistant oil (GOST 18852) permissible temperature	250

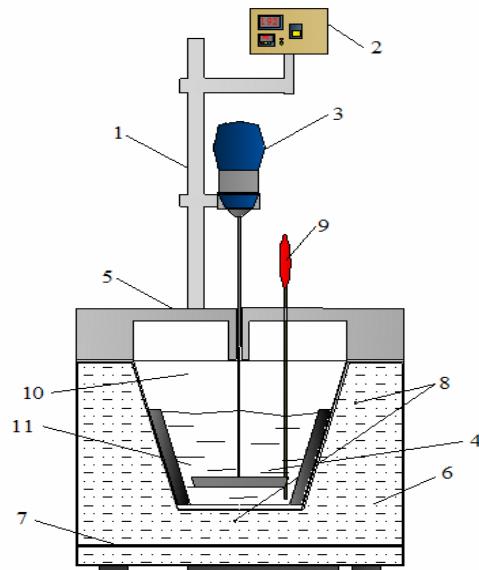


**Fig. 1.** Laboratory blade mixer (side-view)

1 - tripod, 2 - control unit, 3 - electric motor, 4 - blade agitator, 5 - oil thermostat, 6 - oil tank, 7 - electric tensor, 8 - thermocouple in the oil thermostat, 9 - thermocouple for modified bitumen, 10 - Metal container according to DSTU 3277, 11 - bitumen binder

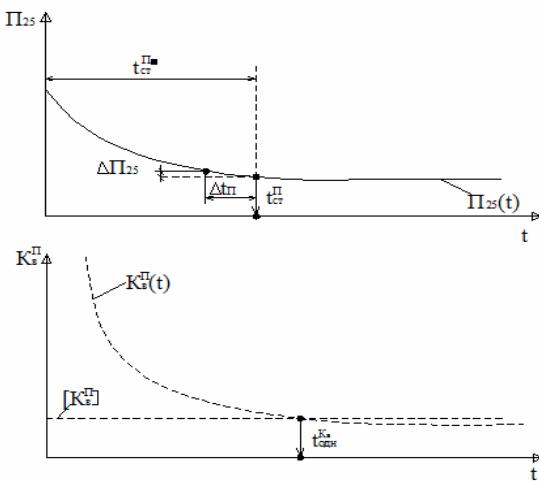

**Fig. 2.** Defining  $t_{3M}$  – time for mixing bitumen with polymer, using laboratory blade mixer on the basis of changes in penetration  $\Pi_{25}(t)$  and coefficient of penetration variation  $K_B^{\Pi}(t)$  depending on mixing time  $t_{3M}$  when  $t_{odn}^{K_B^{\Pi}} \geq t_{cr}^{\Pi}$

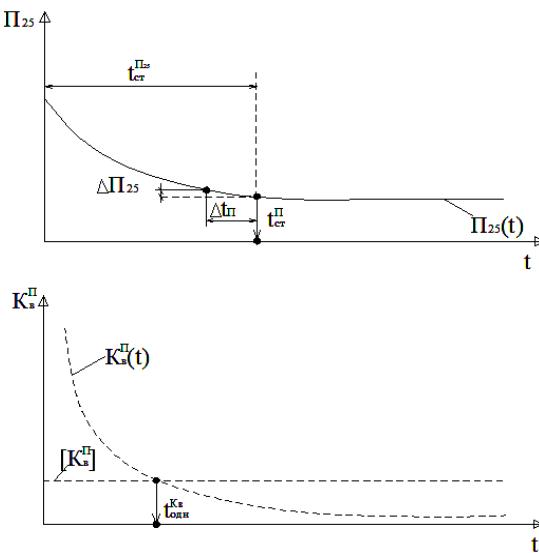


**Fig. 3.** time for mixing bitumen with polymer, using laboratory blade mixer on the basis of changes in penetration  $\Pi_{25}(t)$  and coefficient of penetration variation  $K_B^{\Pi}(t)$  depending on mixing time  $t_{3M}$  when  $t_{odn}^{K_B^{\Pi}} \leq t_{cr}^{\Pi}$

Fig. 2. presents a case where penetration stabilization properties of bitumen are achieved faster than uniformity. In this case, the time to achieve maximum coefficient of variation for penetration  $K_B^{\Pi}(t)$  corresponds to time  $t_{odn}^{K_B^{\Pi}}$ . It is larger than the time which corresponds to the completion of penetration stabilization. Therefore, the process of completing of bitumen modification with poly-

mers will be when the stabilization time for penetration  $t_{cr}^{\Pi}$  will be equal to or exceed mixing time  $t_{odn}^{K_B^{\Pi}}$ .


Fig. 3. presents a case where homogeneity of asphalt binder is reached faster than stabilizing of penetration properties. In this case, the time to achieve maximum coefficient of variation for penetration  $K_B^{\Pi}(t)$  corresponds to time  $t_{odn}^{K_B^{\Pi}}$ . It is smaller than the time which corresponds to the completion of penetration stabilization. Therefore, the process of completing of bitumen modification with polymers will be when mixing time is equal to or greater than penetration stabilization time  $t_{cr}^{\Pi}$ .

A similar scheme is used to determine process of completing of bitumen modification with polymers according to elasticity (Fig. 4 – 5).

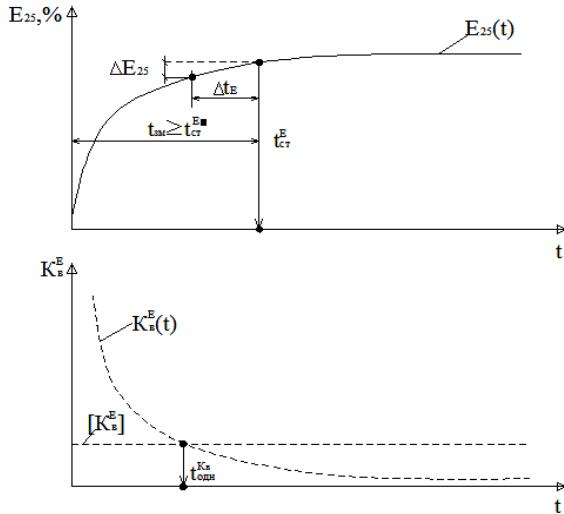

**Fig. 4.** Defining time for mixing bitumen with polymer, using laboratory blade mixer on the basis of changes in elasticity  $E_{25}(t)$  and coefficient of elasticity variation  $K_E^E(t)$  depending on mixing time  $t_{3M}$  when  $t_{odn}^{K_E^E} \leq t_{cr}^E$

The developed method of modified bitumen preparation using laboratory blade mixer allows to determine accurately time and accurate information concerning completion of stabilization properties and homogenization of the modified asphalt binder. After each sampling test results are input into record book and test results are processed [1-6].

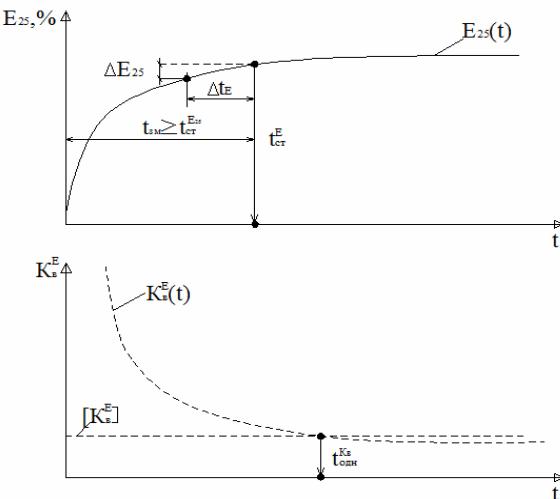

**Fig. 5.** Defining time for mixing bitumen with polymer, using laboratory blade mixer on the basis of changes in elasticity  $E_{25}(t)$  and coefficient of elasticity variation  $K_E^B(t)$  depending on mixing time  $t_{3M}$  when  $t_{\text{одн}} \geq t_{\text{ст}}^E$

The authors conducted tests on Mozyrskogo bitumen BND 90/130, using different amounts of cationic polymer latex Butonal NS198. The test results are shown in Table 2.

**Table 2.** Physico-mechanical properties of bituminous binder according to amount of polymer and modification time

Initial bitumen type, type and amount of polymer, %	Mixing time, T, hour	Penetration $\Pi_{25}$ , mm <sup>-1</sup>	R&B $T_p$ , °C	Elasticity $E_{25}$ , %	Ductility $D_{25}$ , cm	Variation coefficient $K_B^{II}$ , %	Variation coefficient $K_B^E$ , %
BND 90/130	-	97,0	47,0	-	>85	-	-
BND 90/130+ 2% Butonal NS198	1	80,0	52,0	62,0	>80	5,73	3,34
	2	73,0	53,0	67,0	77	3,34	3,09
	3	73,0	54,0	69,0	75	2,74	2,22
	4	72,0	55,0	69,0	72	1,39	1,45
	5	71,0	55,0	69,0	71	1,41	0,84
	6	70,0	55,0	69,0	71	0,82	0,72
BND 90/130+ 4% Butonal NS198	1	77,0	56,0	66,0	74	6,29	3,79
	2	67,0	57,0	70,6	61	4,45	3,56
	3	64,0	57,0	71,0	59	3,13	2,82
	4	62,0	60,0	71,7	59	2,48	2,13
	5	60,0	61,0	72,0	56	1,67	1,39
	6	59,0	61,0	72,3	56	1,30	0,80
BND 90/130+ 6% Butonal NS198	1	75,0	63,0	67,0	60	6,67	4,48
	2	69,0	65,0	71,0	47	2,51	4,23
	3	61,0	67,0	72,3	44	4,10	3,48
	4	57,0	67,5	72,6	43	3,51	2,86
	5	54,0	68,0	72,4	43	2,34	1,67
	6	53,0	68,0	72,5	43	1,89	1,38

## PROCESSING OF TEST RESULTS IS CARRIED OUT ACCORDING TO FOLLOWING RULES

Average value and elasticity measurement of penetration for a given stage of the modification of the formula:

$$\bar{\Pi}_{25} = \frac{\sum_{i=1}^n \Pi_{25i}}{n}$$

and

$$\bar{E}_{25} = \frac{\sum_{i=1}^n E_{25i}}{n}, \quad (1)$$

where:  $\bar{\Pi}_{25}$ ,  $\bar{E}_{25}$  – mean value and flexibility for penetration measurements,

$\Pi_{25i}$ ,  $E_{25i}$  – the value of penetration and resilience of each measurement,

$n$  – number of measurements.

Standard deviation values measured from the mean value determined by the formula:

$$\begin{aligned} \sigma_{\Pi_{25}} &= \sqrt{\frac{\sum_{i=1}^n (\Pi_{25i} - \bar{\Pi}_{25})^2}{n-1}} \\ \text{and} \quad \sigma_{E_{25}} &= \sqrt{\frac{\sum_{i=1}^n (E_{25i} - \bar{E}_{25})^2}{n-1}}. \end{aligned} \quad (2)$$

The coefficient of variation for penetration and elasticity is determined by the formula:

$$\begin{aligned} K_B^{\Pi_{25}} &= \frac{\sigma_{\Pi_{25}}}{\bar{\Pi}_{25}} \cdot 100\% \\ \text{and } K_B^{E_{25}} &= \frac{\sigma_{E_{25}}}{\bar{E}_{25}} \cdot 100\%. \end{aligned} \quad (3)$$

## CONCLUSIONS

1. Relative deviation of penetration bitumen at modification time (1-6 hr.) with feeding 2% Butonal NS198 varies from 1 to 6%, with 4% Butonal NS198 varies from 2 to 12% and with 6% Butonal NS198 from 1 to 13%, respectively.
2. Similarly determined relative deviation of bitumen elasticity at modification time (1-6 hr.) with feeding 2% Butonal NS198 varies from 0.5 to 8.0%, with 4% Butonal NS198 from 0.5 to 7, 0%, and with 6% Butonal NS198 varies between 0.5 and 6.0% respectively.
3. Test results are shown in Table 1 indicate that the obtained bituminous binders from initial material using series of different amounts of latex Butonal NS198 have different penetration parameters, but very similar parameters of softening temperature and elasticity. Significant difference of penetration, primarily associated with the rapid process of oxidation and aging of raw materials, as well as modification time and the amount of polymer.
4. The results showed that the optimal bitumen modification at which stabilization of properties and homogenization will be take place, i.e. binder acquires required level of uniformity with latex Butonal NS198, is about 3 hours. For other polymer modification time is set for the above described procedure.

## REFERENCES

1. SOU 42.1- 37641918 - 100:2013. 2003. " Bitumen, modified using laboratory blade mixer. Methods for process control modifications"
2. Zolotarev V.A. 2009. Polymer modified bitumen and asphalt polymer cements. Dorozhnaia tekhnika. 88-95.
3. King G.N., Radovskii B.S. 2004. Properties of polymer bitumen binders in the U.S. and methods of testing. Scientific and Technical Information Kit. Novosti v dorozhnym dele - Issue 6. Moscow. 1-28
4. Hochman L. M. 2004. Complex organic binders based on block copolymers SBS type. Moscow, "Ekoninform" JSC, 510.
5. Kirichek Y.A., Dem'yanenko V.V., Shurebryy O.A. 2008. Experimental study of

- the properties of modified bitumen used in road construction. Bulletin of Prydniprovska State Academy of Construction and Architecture. Dnepropetrovsk, PSABA, Nr 6-7, 14-17.
6. Onishchenko A.M. 2008. Improving durability of asphalt layers by the use of polymer latexes. Theses Candidate of sciences 05.22.11. Kyiv, 229.
  7. DSTU B V.2.7-135:2007. 2007. "Bitumen modified with polymers. Specifications" Zolotarev V.A., Mozgovoy V.V., Zhdanyuk V.K., and other.
  8. Kulalaeva N., Mikhailyuk V., Petrov I. 2012. Research of application of nanotechnology to clean oily water. MOTROL, Vol. 14, Nr 3, 74-84.
  9. Gorbenko E., Streltsov V., Gorbenko N. 2013. Innovative technology of production of vegetable oil. MOTROL, 125-131.
  10. Polishchuk V., Lanovoi A. 2012. Practical methods for evaluating the performance and the need for development of the road network. MOTROL, 69-78.
  11. Chausov N., Wildemann V., Pilipenko A. 2012. Modelling the behavior of plastic materials under complex loads. MOTROL, 191-200.
  12. Anna Maria Klepacka, Jarosław Osiak, Małgorzata Powałka, Jacek Skudlarski. 2013. Krajowe wykorzystanie surowców rolnych do produkcji biopaliw transportowych. MOTROL, 63-67.
  13. Voitov V., Kravtsov, A., Sysenko I. 2013. Prospects for the use of vegetable oils for the manufacture of lubricants and fluids. MOTROL, 54-61.
  14. Sukach M., Filonov. Y. 2012. Stand for research slit digging podgeosinteticheskim pressure. MOTROL, Vol. 14, Nr 3, 120-126.

МЕТОДИКА МОДИФИКАЦИИ  
БИТУМА РАЗНЫМИ ПОЛИМЕРАМИ

**Аннотация.** Важным этапом процесса приготовления модифицированных битумов является подбор их состава и проверка эффективности действия разных полимеров. Поэтому, лопастные смесители нашли широкое применение, как в промышленных, так и в лабораторных условиях для эффективной модификации битума полимерами. Разработанная методика приготовления позволяет точно определить время завершения процесса модификации в различных технологических параметров (температуры, скорости перемешивания и содержания модификатора) и достоверную информацию относительно завершения стабилизации свойств и гомогенизации

модифицированного битумного вяжущего. Результаты исследований показали, что оптимальное время модификации битумного вяжущего, при котором состоятся как стабилизация свойств так и гомогенизации, то есть вяжущее приобретет необходимый уровень

однородности латексом Butonal NS198 составляет около 3 часов.

**Ключевые слова:** трещиноустойчивость, колеестойчивость, сдвигостойчивость, водостойкость, битум модифицированный полимером, лабораторный лопастной смеситель, гомогенизация.